

AN EXPERIMENTAL STUDY ON FLEXURAL AND ELASTIC BEHAVIOUR OF FLYASH BASED GEOPOLYMER CONCRETE WITH GGBS

USHA.M

M.E Construction Engineering and Management: Dept. of Civil Engineering
T.S.M Jain College of Technology,
Kallakurichi, Tamilnadu
Ushacivil07@gmail.com

ABSTRACT

Ordinary Portland cement concrete is one of the most widely used construction materials being used in infrastructure development throughout the world. cement is the main ingredient in the production of concrete. carbon dioxide and green house gases are produced from industries during the production of cement. The production of cement emits for about equal amount of carbon dioxide. It also produces global warming. In order to reduce the usage of cement, supplementary cementing materials like fly ash and GGBS and instead of water, Alkali solution have been introduced in the name of Geopolymer concrete. Geopolymer concrete is an inorganic polymer composite. In this paper an attempt is made to study flexural and elastic properties of geopolymer concrete replacing with GGBS in 5 different percentages as (100% , 0%), (90% , 10%), (80% , 20%), (70% , 30%), (60% , 40%). Sodium silicate (103kg/m^3) and sodium hydroxide of 8 molarity (41kg/m^3) solutions were used as alkaline activators in all different mixes. The investigations were carried for the Compressive test, Tensile test, Flexural strength test, Modulus of Elasticity, Poisson's ratio on the concrete specimens. The specimens were cured at ambient temperature and tested at 7th and 28th days.

Introduction

Concrete is one of the most widely used construction material. Production of Portland cement is currently exceeding 2.6 billion tons per year worldwide and growing at 5 percent annually. Portland cement fabrication is a major donor to carbon-di-oxide emissions as an estimated five to eight percent of all human-generated atmospheric carbon-di-oxide worldwide comes from the concrete industry. The global warming is caused by the emanation of greenhouse gases, such as carbon-di-oxide, to the atmosphere by human activities. Among the greenhouse gases, carbon-di-oxide contributes about 65% of global warming. The amount of the carbon dioxide released during the manufacture of Ordinary Portland Cement is approximately one ton

for every ton of Ordinary Portland Cement produced. The emission of CO_2 to atmosphere is reduced above 80% by Geo Polymer technology.

New supplementary cementitious materials and pozzolanas such as ground blast furnace slag, metakaolin, fly ash, and silica fume are being increasingly used as additives along with new varieties of superplasticizers. These have helped in producing very efficient high-performance concretes.

Geopolymer Concrete

In this work, alkaline activator is used as the binder, instead of Portland or any other cement paste, to produce normal concrete. The fly ash-based geopolymer paste binds with free coarse aggregates, fine aggregates and other un-reacted materials together to form the fly ash based geopolymer concrete, with or without the presence of admixtures. The manufacture of geopolymer concrete is carried out using the usual manufacturing methods. The silicon and the aluminum is with low calcium (Class F) fly ash are activated by a combination of alkaline solution like sodium hydroxide and sodium silicate solutions to form the fly ash based geopolymer paste that binds the loose aggregates and other un-reacted materials.

Origin

Geopolymer, also known as 'inorganic polymer', has emerged as a 'green' binder with wide potentials for manufacturing sustainable materials. The silicon (Si) and the aluminium (Al) in a source material of geological origin or in by-product materials such as fly ash and GGBS to produce binders.

Constituents of Geo-polymer Concrete

Ingredients required for creation of geopolymer binders are:

- Geopolymeric source materials such as fly ash and GGBS.

- Aggregate system consisting of free fine and coarse aggregates
- Alkaline Activator Solution

Geopolymerization

Geopolymers are part of polymer science, chemistry and technology that forms one of the major areas of materials science. Polymers are either organic material, i.e. carbon-based, or inorganic polymer, for example silicon-based.

Necessity of Geopolymer Concrete

As per the present world statistics, every year around 260, 00, 00,000 tons of cement is required. This quantity will be increased by 25% within a span of next 10 years. Since the limestone is the main source material for the OPC an acute shortage of limestone may come after 25 to 50 years. More over while producing one ton of cement, approximately one ton of Co₂ will be emitted to the atmosphere, which is a major threat for the environment. Hence it's essential to find alternative binder.

Objectives

- To make a concrete without using cement and water (i.e. Geopolymer concrete).
- concrete with percentage replacement of GGBS.
- To evaluate the optimum mix proportion of Geo-polymer concrete with fly ash replaced in various percentage by GGBS.
- To compare the cost variation of geopolymer concrete with normal concrete.

Materials

Fly ash

Fly ash is a byproduct from burning pulverized coal in electric power generating plants. During combustion, mineral impurities in the coal. Fly ash is a powdery form. Fly ash is the main by product created from the combustion of coal in coal-fired power plants.

Table 1. Chemical composition

Oxides	Percentage
SiO ₂	52.0
Al ₂ O ₃	33.9
Fe ₂ O ₃	4.0
CaO	1.2
K ₂ O	0.83
Na ₂ O	0.27
MgO	0.81
SO ₃	0.28
LOI	6.23
SiO ₂ /Al ₂ O ₃	1.5

Table 2. Properties of Fly ash

SNo.	Property	Value
1	Specific Gravity	2.44
2	Fineness	227.8 g/m ²
3	Fineness Modulus	5
4	Density	1029.7 Kg/m ³

Ground Granulated Blast Furnace Slag

The addition of G.G.B.S in Geo-Polymer Concrete increases the strength of the concrete and also curing of Geo-Polymer concrete at room temperature is possible.

Table 3. Properties of GGBS

S No.	Property	Value
1	Specific Gravity	2.58
2	Fineness	202.7 g/m ²
3	Fineness Modulus	7
4	Density	2067.06 Kg/m ³

Table 4. chemical composition

Chemical constitution	Cement (%)	GGBS (%)
CaO	65	40
SiO ₂	20	35
Al ₂ O ₃	5	10
MgO	2	8

Fine aggregate

The fine aggregate used in the project was locally supplied and conformed to grading zone II as per IS: 383:1970.

Table 5. Properties of fine aggregates

S.No	Characteristics	Values
1.	Type	Uncrushed (natural)
2.	Specific gravity	2.54
3.	Bulk Density	1668 kg/m ³
4.	Fineness modulus	2.76
5.	Grading zone	Zone II

Coarse aggregate

Locally available coarse aggregate having the maximum size of (10 - 20mm) were used in this project.

Table 6. Properties of coarse aggregates

S.No	Characteristics	Values
1.	Type	Crushed
2.	Specific gravity	2.6
3.	Bulk Density	1765 kg/m ³
4.	Fineness modulus	6.45
5.	Maximum size	20mm

Alkaline Liquid

A combination of alkaline silicate solution and alkaline hydroxide solution was chosen as the alkaline liquid. Sodium-based solutions were chosen because they were cheaper compare to the Potassium-based solutions.

Sodium Hydroxide

The sodium hydroxide solids were of a laboratory grade in pellets form with 99% purity, obtained from local suppliers. The sodium hydroxide (NaOH) solution was prepared by dissolving the pellets in water.

Sodium Silicate

Sodium silicate solution (water glass) obtained from local suppliers was used. The chemical composition of the sodium silicate solution was Na₂O=8%, SiO₂=28%, and water 64% by mass.

Superplasticizer

Addition of superplasticizer to stiff concrete mix reduces its water reducing efficiency. In this investigation, a superplasticizer CONPLAST SP 430 complies with BIS : 9103-1999 and BS : 5075 part 3 and ASTM C 494 has been used.

Preparation of Alkaline Activator Solution

The mixture of sodium silicate solution and sodium hydroxide solution forms the alkaline liquid. sodium-based solutions were chosen because they were cheaper than potassium-based solutions. The Alkali activator solution has to be prepared 24 hours advance before use. Sodium hydroxide pellets have to be distilled in water and then mixed with sodium silicate solution.

Geo-polymer mix design value

The design compressive strength is taken as 45MPa

Constituents	Density (kg/m ³)
Coarse aggregate	1294
Fine aggregate	554
Fly ash	408

Sodium silicate	103
Sodium hydroxide	41
Super plasticizer	6.12

Casting and Curing of test specimens

Each specimen was casted in 3layers and each layer received 25 strokes of compaction by standard compaction rod for concrete. After 24 hours the specimens were demoulded and placed into curing till age of testing to be done.


Testing of specimen

Compressive Strength test

All the cubes were tested under drying condition, after drying the surface of the specimens containing no moisture content. Using compression testing machine of 200Tonnes capacity as per IS: 516-1959 code. From the test results, it was observed that the maximum compressive strength was obtained for mix with 30% GGBS and 70% flyash.

Table 7. compressive test results

MIX ID	FLYASH (%)	GGBS (%)	Compressive strength N/mm ²	
			7 th Day	28 th Day
M1	100	-	11.88	17.55
M2	90	10	17.09	22.97
M3	80	20	24.85	35.32
M4	70	30	38.33	44.58
M5	60	40	40.77	46.55
CM	-	-	26.67	37.85

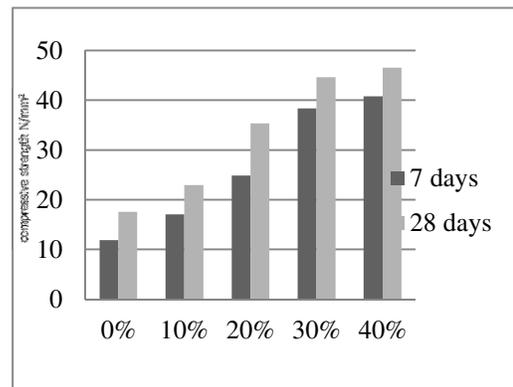


Bar chart of compressive strength

Split Tensile Strength test

As per IS 516-1959 the split tensile strength of specimen were calculated. It was observed that the maximum split tensile strength was obtained for mix M2 with 30 % GGBS and 70% flyash

Table 8. split tensile test results

MIX ID	Binder (%)		Split tensile strength (N/mm ²)
	FLYASH	GGBS	
M1	100	-	2.15
M2	90	10	4.25
M3	80	20	4.97
M4	70	30	5.67
M5	60	40	7.13
CM	-	-	5.25

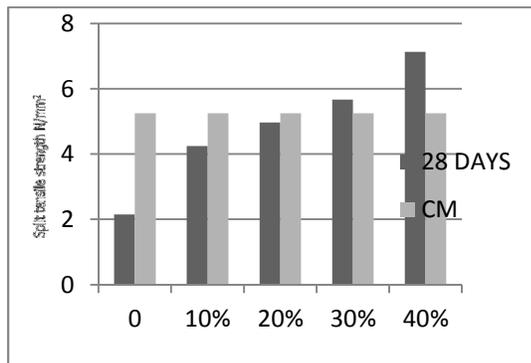

Bar chart of split tensile strength

MIX ID	Binder (%)		Modulus of Elasticity (GPa)
	FLYASH	GGBS	
M1	100	-	27.33
M2	90	10	30.73
M3	80	20	32.54
M4	70	30	33.76
M5	60	40	35.68

Flexural Strength test

As per IS 516-1959, the flexural strength has been calculated using the formula


$$f_b = \frac{Pl}{bd^2}$$

From the test results, it was observed that when the percentage of GGBS increases, the flexural strength of concrete also increases. On the contrary, the

strength decreases when the percentage of flyash increases.

Table 9. flexural strength results

MIX ID	Binder (%)		Flexural strength (N/mm ²)
	FLYASH	GGBS	
M1	100	-	3.16
M2	90	10	4.47
M3	80	20	5.28
M4	70	30	6.10
M5	60	40	6.97
CM1	-	-	5.65

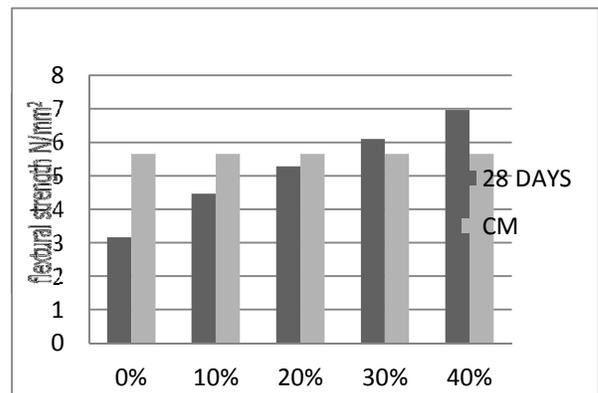

Bar chart of Flexural strength

Elastic Properties

Modulus of Elasticity

Young's modulus is a measure of the stiffness of an elastic isotropic material. It is defined as the ratio of the stress along an axis over the strain along that axis in the range of stress in which Hooke's Law. Modulus of elasticity is determined by subjecting a cube or cylinder specimen to uniaxial compression and measuring the deflections by means of LVDT's connected with dial gauges fixed between certain gauge lengths. The average value of modulus of elasticity determined by means of an extensometer as per IS 516 -1959.

Modulus of Elasticity = stress/strain.

Table 9. modulus of elasticity results

Poisson's Ratio

Poisson's ratio is the negative ratio of transverse to axial strain when the material is compressed in one direction. It usually tends to expand in the other two directions perpendicular to the direction of compression. This phenomenon is called Poisson effect. The Poisson ratio is the fraction of expansion by the

fraction of compression, for small values of these changes.

Poisson's ratio = lateral strain/linear strain (Or) 1/m.

Table 10. poisson's ratio results

MIX ID	Binder (%)		Poisson's ratio
	FLYASH	GGBS	28 th Day
M1	100	-	0.26
M2	90	10	0.24
M3	80	20	0.23
M4	70	30	0.22
M5	60	40	0.19

Conclusion

Based on the experimental investigation the following conclusions are listed below:

- The optimum replacement level of fly ash by GGBS in GPC has been carried out.
- Water absorption property is lesser than the nominal concrete
- Achieving strength in a short time i.e. 70% of the compressive strength in first 4 hours of setting.
- From the test results, it was observed that the maximum strength was obtained for mix with 30% GGBS and 70% flyash.
- The present studies indicate that as strength of concrete increases there is decrease in the average value of Poisson's ratio.
- The Modulus of elasticity values increases with increase in compressive strength of geopolymer concrete.
- The obtained elastic properties values are in pair with the values developed for ordinary Portland cement concrete.

References

1. R.Anuradha, R.Venkatasubramani and B.V.Rangan(2012)“Modified guidelines for geopolymer concrete mix design using Indian Standard” – Asian Journal of Civil Engineering(Building and Housing), Volume 13.
2. M. I. Abdul Aleem, P. D. Arumairaj,(2013) “GEOPOLYMER CONCRETE-A REVIEW”, International Journal of

Engineering Sciences & Emerging Technologies, Feb 2012. ISSN: 2231 – 6604 Volume 1, Issue 2.

3. T.Bakharev ,J.G.Sanjayan and Y.B.Chen,(2003), Resistance of alkali-activated slag concrete to acid attack, Cement Concrete Research 33 pp. 1607–1611.
4. Prof.M.A.Bhosale, Prof.N.N.Shinde(2012), “Geopolymer Concrete by Using Fly Ash in Construction”, IOSR Journal of Mechanical and Civil Engineering (IOSRJMCE) ISSN : 2278-1684 Volume 1, Issue 3 (July-August 2012), PP 25-30.
5. Dattatreya J K, Rajamane NP, Sabitha D, Ambily P S, Nataraja MC(2011), “Flexural behaviour of reinforced Geopolymer concrete beams”, INTERNATIONAL JOURNAL OF CIVIL AND STRUCTURAL ENGINEERING Volume 2, No 1, 2011, ISSN 0976 – 4399
6. DjwantoroHardjito, Steenie E. Wallah, Dody M.J. Sumajouw, and B.V. Rangan(2004) “FACTORS INFLUENCING THE COMPRESSIVE STRENGTH OF FLY ASH-BASED GEOPOLYMER CONCRETE” Civil Engineering Dimension, Vol. 6, No. 2, 88–93, September 2004 .
7. DjwantoroHardjito, Steenie E. Wallah, Dody M. J. Sumajouw, and B.VijayaRangan(2013) “On the Development of Fly Ash-Based Geopolymer Concrete”, ACI materials journal technical paper aci materials journal technical paper.
8. DjwantoroHardjito(2005), “Studies on Fly Ash-Based Geopolymer Concrete” Concrete in Australia, vol. 28, no. 4, pp. 24-29.
9. S.J.Foster, T.S.Ng, Futures in Mechanics of structures and materials (2009) ‘Development of high performance Geopolymer concrete’.
10. P.Ganapati Naidu, A.S.S.N.Prasad,P.V.V.Satayanarayana(2012)“A Study On Strength Properties Of Geopolymer Concrete With Addition Of

G.G.B.S” International Journal of Engineering Research and Development Volume 2, Issue 4, PP. 19-28.

11. R. B. Khadiraniakar and Shankar H. Sanni(2014), “Stress Strain Characteristics for Geopolymer Concrete – An Experimental Approach” CACE Volume 2, Issue 2 Apr. 2014 PP. 44-47.
12. Prof.PratapKrishnarao(2013), “Design of Geopolymer Concrete” International Journal of Innovation Research in Science, Engineering and Technology (IJIRSET) Volume 2 Issue 5.
13. K.Parthiban,K.Saravanarajamohan,S.Shobana,A.AnchaBhaskar(2013), “Effect of Replacement of Slag on the Mechanical Properties of Fly Ash Based Geopolymer Concrete” International Journal of Engineering and Technology (IJET) Volume 5.
14. Dr.P.Priya Rachel (2015) “Study on Geopolymer Concrete Block”, Volume : 5 | Issue : 4 | April 2015 | ISSN - 2249-555X
15. D.B.Rajiwala, H.S.Patil(2011)“Geopolymer Concrete : A Concrete Of Next Decade” Journal of Engineering Studies and Research (JERS) Vol. II Issue.
16. Rajiwala D.B, PatilH(2013) “GEOPOLYMER CONCRETE: A CONCRETE OF NEXT DECADE” Journal of Engineering Research and Studies.
17. S.SundarKumar, J.Vasugi,P.S.Ambily and B.H.Bharatkumar(2013), “Development and Determination of Mechanical Properties of Fly Ash And Slag Blended Geo Polymer Concrete” International Journal of Scientific & Engineering Research, Volume 4, Issue 8.

IS CODES:

- IS 10262:2009; Mix design of concrete.
- IS 456:2000; Plain and Reinforced concrete code of Practice.

- IS 383:1970; Specification for coarse and fine aggregates from natural sources for concrete
- IS 516: 1959; Methods of tests for Strength of concrete